

Theory of the Reentrant Charge-Order Transition in the Manganites

C. Stephen Hellberg[†]

Center for Computational Materials Science, Naval Research Laboratory, Washington, DC 20375
(February 1, 2008)

A theoretical model for the reentrant charge-order transition in the manganites is examined. This transition is studied with a purely electronic model for the e_g Mn electrons: the extended Hubbard model. The electron-phonon coupling results in a large nearest-neighbor repulsion between e_g electrons. Using a finite-temperature Lanczos technique, the model is diagonalized on a 16-site periodic cluster to calculate the temperature-dependent phase boundary between the charge-ordered and homogeneous phases. A reentrant transition is found. The results are discussed with respect to the specific topology of the 16-site cluster.

The manganites have a very rich phase diagram that includes ferromagnetic, antiferromagnetic, and charge-ordered phases [1–3]. Various theoretical models have been used to explain different aspects of this phase diagram [4–7].

In its simplest incarnation, the charge-ordered (CO) phase occurs at hole doping $x = 1/2$ with equal amounts of Mn^{3+} and Mn^{4+} ordered in real space in a checkerboard pattern. The oxygens relax away from the Mn^{3+} ions and towards the Mn^{4+} ions, thus providing a repulsive potential between Mn^{3+} ions (or equivalently between Mn^{4+} ions). The potential energy gain exceeds the kinetic energy loss due to the formation of this insulating state [8].

When observed, the CO is generally the lowest temperature phase, but recently the CO phase has been seen to melt with decreasing temperature in $\text{Pr}_{0.65}(\text{Ca}_{0.7}\text{Sr}_{0.3})_{0.35}\text{MnO}_3$ [9] and $\text{LaSr}_2\text{Mn}_2\text{O}_7$ [10]. The lowest temperature phase is metallic, and the CO insulator is only observed at intermediate temperatures. A reentrant transition has been obtained theoretically using extended Hubbard models both with electron-phonon interactions [11] and without electron-phonon interactions [12].

In this paper, we study the charge-order transition in the extended Hubbard model (without electron-phonon interactions) on the two-dimensional square lattice. Previous work [12] solved this model in infinite spatial dimensions, resulting in finite entropy (due to the spins) at $T = 0$ in the CO phase, so a reentrant transition was guaranteed to be found. In the infinite two-dimensional square lattice, the spins will order into a Néel state with zero entropy at $T = 0$.

The Hamiltonian is given by

$$H = t \sum_{\langle ij \rangle \sigma} (c_{i\sigma}^\dagger c_{j\sigma} + \text{h.c.}) + U \sum_i n_{i\uparrow} n_{i\downarrow} + V \sum_{\langle ij \rangle} n_i n_j, \quad (1)$$

where $c_{i\sigma}^\dagger$ ($c_{i\sigma}$) creates (annihilates) an electron with spin σ on site i , $n_{i\sigma}$ is the number operator with spin σ on site i , and $n_i = n_{i\uparrow} + n_{i\downarrow}$. The hopping amplitude is t , $\langle ij \rangle$

enumerates nearest neighbor sites on the two-dimensional square lattice, U is onsite repulsion, and V is the nearest-neighbor repulsion. The non-interacting bandwidth on the two-dimensional square lattice is given by $W = 8|t|$; we set $U = W$ and vary V at quarter filling (one electron for every two sites). For small V , we expect the ground state will be a homogeneous Fermi liquid. For large V , the electrons will crystallize in a checkerboard pattern to avoid occupying neighboring sites.

We solve the Hamiltonian (1) on a 4×4 cluster using a recently developed finite-temperature Lanczos technique [13,14]. We choose periodic boundary conditions resulting in a closed Fermionic shell in the non-interacting limit [15]. In each symmetry sector, we perform $N_L = 4000$ Lanczos steps. We eliminate spurious eigenvalues [16], leaving more than 2000 real eigenvalues in each sector, but not all of these will be converged. The extreme eigenvalues (lowest and highest) converge first [14]. From these eigenvalues, we compute the susceptibility

$$\chi = \frac{1}{N} \frac{\partial E}{\partial V}, \quad (2)$$

where $N = 16$ is the number of sites. The susceptibility χ is equivalent to the nearest-neighbor pair correlation function by the Kubo formula. In the homogeneous phase χ is large, but in the CO phase where there is only a small probability of finding electrons on neighboring sites, χ is small.

The susceptibility (2) for five different temperatures is plotted in Fig. 1. For all temperatures shown, χ is large at small V in the homogeneous phase, decreases continuously with increasing V , and flattens out at a small value in the CO phase at large V . To determine the boundary between the homogeneous and CO phases, we pick a critical value of $\chi_c = 0.1$ for the phase boundary. We choose this value to coincide approximately with the maximum of $\partial^2 \chi / \partial V^2$. A different value of χ_c results in a phase boundary that is qualitatively the same: for all reasonable values of χ_c , the phase boundary first shifts to smaller V as the temperature is raised from zero and then moves to larger V in the high-temperature regime, characteristic of a reentrant transition.

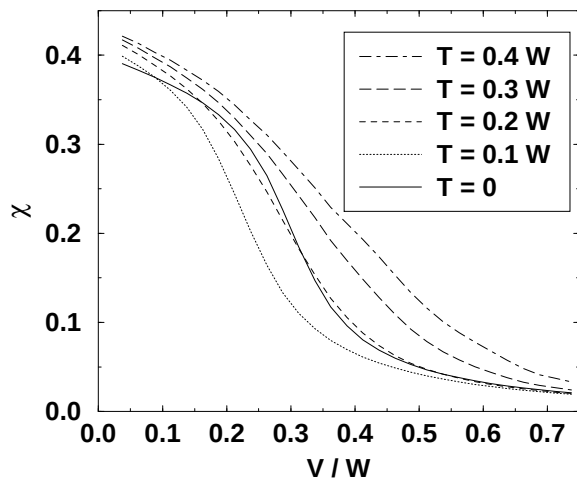


FIG. 1. Temperature dependence of the susceptibility as a function of the nearest-neighbor repulsion V (in units of the bandwidth $W = 8|t|$) for the 4×4 periodic cluster at $U = W$. The susceptibility varies continuously even at $T = 0$ (solid curve). The susceptibility is large in the homogeneous phase (small V) and small in the CO phase (large V). With increasing temperature, the susceptibility first shifts to smaller V then to larger V , indicating a reentrant transition.

The phase diagram calculated from the point where $\chi(V, T) = \chi_c = 0.1$ is shown in Fig. 2. Reentrant behavior is seen for $0.31 \lesssim V/W \lesssim 0.37$. For V in this range, the ground state is homogeneous, but a CO phase exists at intermediate temperatures.

The 4×4 system has no entropy in either the homogeneous or the CO phases, so the phase boundary in Fig. 2 has infinite slope in the $T \rightarrow 0$ limit. However, the CO phase has more low-lying excitations than the homogeneous phase, so in the reentrant region the CO phase becomes favored at intermediate temperatures.

The greater number of low-lying excitations in the CO phase may be at least partially due to the topology of the 4×4 periodic cluster used. The homogeneous phase will have the usual Fermi-liquid excitations. In the CO phase, the electrons order in a checker-board pattern. The spins interact via a fourth order superexchange process [17,18]. A given spin can interact both with its diagonal neighbor and with its neighbor two steps away either horizontally or vertically. On the infinite lattice, the interaction with the diagonal neighbor is 4 times as strong as the interaction with the horizontal/vertical neighbor because there are 4 times as many diagonal superexchange paths. Thus the spin system is equivalent to the extended antiferromagnetic Heisenberg model on a square lattice with $J_1 = 4J_2$, where J_1 is the nearest-neighbor interaction and J_2 is the next-nearest-neighbor interaction. Extensive numerical calculations have shown that this Heisenberg model forms a Néel state at $T = 0$ [19,20].

Because two steps to the left is the same as two steps to the right (and the same for up and down), the 4×4 pe-

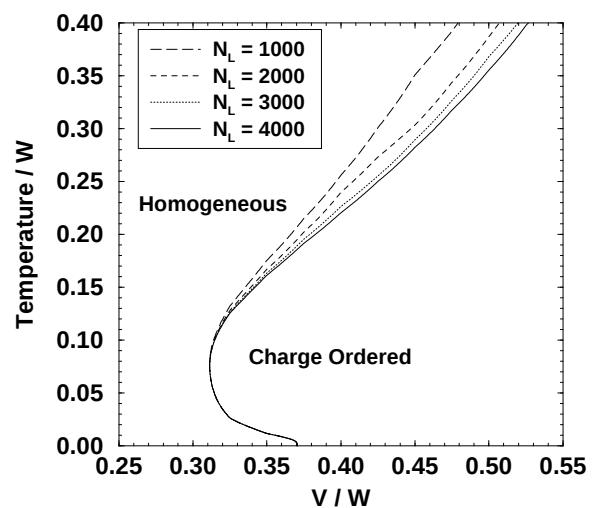


FIG. 2. Phase diagram for the model with $\chi_c = 0.1$. There is clear reentrant behavior around $V/W \approx 0.35$. The four curves correspond to different numbers of Lanczos steps. Runs with more Lanczos steps result in more eigenvalues, and thus are accurate to higher temperatures. The $N_L = 4000$ run is clearly accurate well into the high-temperature homogeneous phase in the reentrant region.

riodic cluster is equivalent to a hypercubic 2^4 cluster [21]. Thus the diagonal superexchange coupling is the same as the horizontal/vertical coupling. So the CO Néel state on this particular cluster is strongly frustrated and may not form. This could contribute to the greater density of low lying states in the CO phase than in the homogeneous phase.

Smaller periodic clusters have even more severe finite-size problems. We decided to work with the 4×4 cluster because it is the largest system with a manageable Hilbert space. Even with all symmetries applied, the largest Hamiltonian matrices were larger than 2.0×10^5 (the matrices are very sparse, with only about 30 non-zero elements in each row or column). The Hilbert space diverges exponentially with the number of sites in the cluster. The next largest cluster with an even number of electrons has 20 sites and has irreducible sectors with Hilbert spaces larger than 2.4×10^8 , more than 1000 times larger than those of the 16-site system.

In summary, we have examined the reentrant charge order transition in a simple model for the manganites, the extended Hubbard model in two dimensions. We computed the low-lying eigenvalues of the model on a 16-site periodic cluster, and used the susceptibility with respect to the nearest-neighbor repulsion to compute the low-temperature phase boundary between the homogeneous and charge-ordered phases. Like previous results on this model in infinite dimensions, we find a parameter region where the model shows reentrant behavior. The reentrant region may be partially an artifact of the small cluster used, which frustrates the formation of Néel spin

order in the charge ordered state.

This work was supported by the Office of Naval Research. Computations were performed on the SGI Origin 2000 at the ASC DoD Major Shared Resource Center.

[†] Electronic address: hellberg@dave.nrl.navy.mil

- [1] P. Schiffer, A. P. Ramirez, W. Bao, and S.-W. Cheong, Phys. Rev. Lett. **75**, 3336 (1995).
- [2] A. P. Ramirez, J. Phys. Cond. Mat. **9**, 8171 (1997).
- [3] S. Mori, C. H. Chen, and S.-W. Cheong, Nature **392**, 473 (1998).
- [4] A. Moreo, S. Yunoki, and E. Dagotto, Science **283**, 2034 (1999).
- [5] G. Jackeli, N. B. Perkins, and N. M. Plakida, Phys. Rev. B **62**, 372 (2000).
- [6] D. Khomskii, Physica B **280**, 325 (2000).
- [7] J. van den Brink, G. Khaliullin, and D. Khomskii, Phys. Rev. Lett. **83**, 5118 (1999).
- [8] M. Vojta, R. E. Hetzel, and R. M. Noack, Phys. Rev. B **60**, R8417 (1999).
- [9] Y. Tomioka, A. Asamitsu, H. Kuwahara, and Y. Tokura, J. Phys. Soc. Japan **66**, 302 (1997).
- [10] T. Kimura, R. Kumai, Y. Tokura, J. Q. Li, and Y. Matsui, Phys. Rev. B **58**, 11081 (1998).
- [11] Q. Yuan and P. Thalmeier, Phys. Rev. Lett. **83**, 3502 (1999).
- [12] R. Pietig, R. Bulla, and S. Blawid, Phys. Rev. Lett. **82**, 4046 (1999).
- [13] C. S. Hellberg, W. E. Pickett, L. L. Boyer, H. T. Stokes, and M. J. Mehl, J. Phys. Soc. Japan **68**, 3489 (1999).
- [14] C. S. Hellberg, in *Computer Simulation Studies in Condensed Matter Physics XIII*, edited by D. P. Landau, S. P. Lewis, and H. B. Schüttler (Springer-Verlag, Heidelberg, Berlin, 2000).
- [15] C. S. Hellberg and E. Manousakis, Phys. Rev. B **61**, 11787 (2000).
- [16] J. K. Cullum and R. A. Willoughby, *Lanczos Algorithms for Large Symmetric Eigenvalue Computations* (Birkhauser, Boston, 1985).
- [17] J. B. Goodenough, *Magnetism and the Chemical Bond* (Wiley, New York, 1993), Chap. IIIC.
- [18] E. Manousakis, Rev. Mod. Phys. **63**, 1 (1991).
- [19] H. J. Schulz, T. A. L. Ziman, and D. Poilblanc, J. Phys. I (Paris) **6**, 675 (1996).
- [20] R. R. P. Singh, W. Zheng, C. J. Hammer, and J. Oitmaa, Phys. Rev. B **60**, 7278 (1999).
- [21] E. Dagotto, R. Joynt, A. Moreo, S. Bacci, and E. Dagliano, Phys. Rev. B **41**, 9049 (1990).